


PHOTODESORPTION AND HIGHER-ORDER ASSEMBLIES OF POTASSIUM POLYTITANATE FOR WATER TREATMENT

**Submitted by
Mohammad Shahid**

**A thesis submitted in fulfilment of the requirements for the degree of
Doctor of Philosophy**

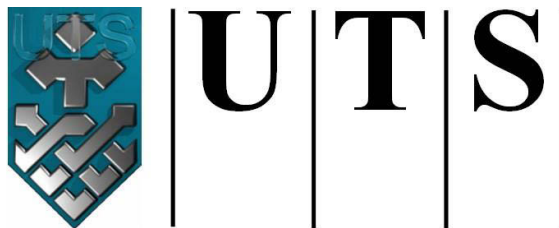

**University of Technology Sydney
FACULTY OF ENGINEERING**

2015

Certificate of Authorship

I certify that the work in this thesis has not previously been submitted for a degree nor has it been submitted as part of requirements for a degree except as fully acknowledged within the text.

I also certify that the thesis has been written by me. Any help that I have received in my research work and the preparation of the thesis itself has been acknowledged. In addition, I certify that all information sources and literature used are indicated in the thesis.

Signature of Student:

A handwritten signature in black ink, appearing to be 'D. G. H.', written over a horizontal line.

Date: 07/07/2015

Acknowledgments

Foremost, I would like to express my sincere gratitude to my principal supervisor A/Prof. Ho Kyong Shon for his continuous support, encouragement and guidance throughout my journey at UTS. I will always remember your invaluable mentorship which helped me to achieve my goals. I would also like to thank my co-supervisor Dr Andrew McDonagh for his advice, motivation and immense knowledge. His wisdom and guidance helped me to deal with several issues during my doctoral candidature.

Moreover, I would like to acknowledge Dr Ibrahim El Saliby and Dr Leonard D. Tijing for their help in the design, implementation and revision of this research thesis. Their kind support helped me bring this research to its end. I would also like to express my appreciation to faculty members Prof. Saravanmuthu Vigneswaran, Prof. Huu Hao Ngo, A/Prof Jaya Khandaswamy and Dr Robert McLaughlan for their support and engagement in the CTWW.

I am also grateful to UTS research fellows Dr Sherub Phuntsho, Dr Tien Than, and Dr Ghausul Hussain for their assistance concerning several issues. Special thanks must go to all my colleagues and beloved friends, Johir, Laura, Tahir, Aaron, Soleyman, Fouzy for their friendship and help during the last four years.

Lastly, I also would like to thank UTS-IRS and APA-LP for providing scholarship and financial support that made for the completion of my thesis possible.

List of Abbreviations

AFM	:	Atomic Force Microscopy
AOPs	:	Advanced Oxidation Processes
BET	:	Brunauer, Emmet and Teller
BJH	:	Barret Joyner Halender
CB	:	Conduction Band
CNTs	:	Carbon Nanotubes
CV	:	Crystal Violet
DO	:	Dissolved Oxygen
DOC	:	Dissolved Organic Carbon
DOM	:	Dissolved Organic Matter
EDS	:	Energy Dispersive X-ray Spectroscopy
EDX	:	Energy Dispersive X-ray
FTIR	:	Fourier Transform Infrared Spectroscopy
HDTMA	:	Hexadecyltrimethylammonium
HMW	:	High Molecular Weight
HOC	:	Hydrophilic Organic Carbon
HP-SEC	:	High Performance Size Exclusion Chromatography
LC-OCD	:	Liquid Chromatography - Organic Carbon Detection
LMW	:	Low Molecular Weight
MB	:	Methylene Blue
PTTF	:	Polytetrafluoro Ethylene
PZC	:	Point of Zero Charge
SEM	:	Scanning Electron Microscope

STM	:	Scanning Tunnelling Microscopy
SWW	:	Synthetic Wastewater
TEM	:	Transmission Electron Microscope
TOC	:	Total Organic Carbon
UV	:	Ultra Violet
VB	:	Valance Band
XRD	:	X-ray diffraction

Table of Contents

Certificate of Authorship	ii
Acknowledgments	iii
List of Abbreviations	iv
Table of Contents	vi
List of Figures.....	xiii
List of Tables	xvi
Abstract.....	xvii
List of publications included in the Thesis	xxii
Other publications during the PhD candidature*	xxiii
Conference papers and presentations	xxiv
Chapter 1: Introduction	1-1
1.1 Nanotechnology for water purification.....	1-2
1.2 Photocatalysis over Titanium dioxide	1-3
1.3 Photodesorption of organic matter	1-5
1.4 Higher-order assemblies of Titania nano structure.....	1-7
1.5 Research objective and scope	1-8
1.6 Thesis Structure	1-9
Chapter 2: Literature review.....	2-1
2.1 Nanotechnology for water treatment	2-2
2.1.1 Current potential applications of nanotechnology for water and wastewater treatment	2-3
2.1.1.1 Adsorption	2-3
2.1.1.2 Membranes and membrane processes	2-7
2.1.1.3 Photocatalysis	2-9

2.1.2	Significance of Nanotechnology in Wastewater Treatment	2-10
2.1.3	Techniques and Instruments used to analysis nanomaterials.....	2-12
2.1.4	Nanotechnology and the challenges	2-14
2.2	Heterogeneous Photocatalysis	2-15
2.2.1	History and overview	2-17
2.2.2	Fundamentals of Photocatalysis.....	2-18
2.2.3	Factor influencing Photocatalytic degradation	2-20
2.2.3.1	Adsorption	2-20
2.2.3.2	Pollutant concentration.....	2-21
2.2.3.3	Photocatalyst loading.....	2-21
2.2.3.4	Effect of pH	2-22
2.2.3.5	Light intensity and radiation time.....	2-23
2.2.3.6	Dissolved oxygen	2-24
2.2.3.7	Temperature.....	2-25
2.2.4	Photo reactor design for water treatment.....	2-25
2.2.5	Kinetics of photocatalysis.....	2-28
2.3	Synthesis methods for higher order assemblies titania.....	2-31
2.3.1	Chemical template synthesis.....	2-33
2.3.2	Electrochemical anodization synthesis	2-35
2.3.3	Hydrothermal method	2-36
2.3.4	Mechanism of Titanate formation via alkali hydrothermal treatment ...	2-38
2.3.5	Influencing factors of hydrothermal method on titania	2-40
2.3.5.1	Titanium source	2-40
2.3.5.2	Type and concentration of alkaline	2-42
2.3.5.3	Temperature and duration.....	2-43

2.3.5.4	Washing procedure	2-45
2.3.5.5	Calcination.....	2-45
2.3.5.6	Assisted hydrothermal synthesis	2-46
2.4	Model water pollutant.....	2-49
2.4.1	Synthetic wastewater	2-49
2.4.2	Crystal violet.....	2-50
2.4.3	Methylene blue	2-51
2.4.4	Lead	2-54
Chapter 3:	Materials and Methodology	3-1
3.1	Materials	3-2
3.1.1	Chemicals.....	3-2
3.1.2	Synthetic Wastewater	3-3
3.1.3	Degussa P25.....	3-3
3.1.4	Crystal Violet.....	3-5
3.1.5	Methylene Blue.....	3-5
3.1.6	Lead Nitrate	3-5
3.2	Synthesis.....	3-6
3.3	Characterisation and Methods	3-6
3.3.1	Scanning Electron Microscope / Energy Dispersive X-ray	3-6
3.3.2	Transmission Electron Microscope	3-7
3.3.3	Specific surface area and pore size measurements	3-7
3.3.4	X-ray Diffractometer	3-7
3.3.5	Malvern Zetasizer	3-8
3.4	Photocatalytic reactors.....	3-8
3.4.1	Photo reactor 1	3-8

3.4.2	Photo reactor 2	3-9
3.4.3	Photo reactor 3	3-10
3.5	Auxiliary Laboratory instruments	3-11
3.6	Analytical equipment and procedures	3-13
3.6.1	UV-vis Spectrophotometer	3-13
3.6.2	Dissolved Organic Carbon Measurement	3-14
3.6.3	LC-OCD.....	3-15
3.6.4	Ion Chromatography	3-15
3.6.5	Metal analyser	3-16
3.7	Data processing.....	3-17
Chapter 4: Photodesorption of Organic Matter from Titanium Dioxide		
Particles in Aqueous Media		4-1
4.1	Introduction	4-2
4.2	Experimental.....	4-4
4.2.1	Materials	4-4
4.2.2	Photoreactor setup.....	4-4
4.2.3	Photodesorption of dissolved organic carbon	4-5
4.3	Results and Discussion	4-6
4.3.1	Flow rate	4-6
4.3.2	UV irradiation	4-8
4.3.3	Effect of TiO ₂ loading.....	4-10
4.3.4	Organic concentration.....	4-11
4.3.5	pH of the solution	4-13
4.3.6	Photodesorption of Specific Organic Compounds.....	4-16
4.3.7	LC-OCD analysis.....	4-18

4.4	Conclusions	4-25
Chapter 5: Synthesis and Characterisation of Potassium Polytitanate for Photocatalytic Degradation of Crystal Violet5-1		
5.1	Introduction	5-2
5.2	Experimental.....	5-3
5.2.1	Materials	5-3
5.2.2	Synthesis of potassium titanate.....	5-4
5.2.3	Characterisation	5-4
5.2.4	Adsorption and photocatalysis.....	5-5
5.2.5	Separation by settling.....	5-6
5.3	Results and Discussion	5-6
5.3.1	Characterisation of potassium titanate.....	5-6
5.3.1.1	SEM/EDX and TEM	5-6
5.3.1.2	Textural Property.....	5-8
5.3.1.3	X-ray Diffraction/EDX.....	5-9
5.3.2	Adsorption of crystal violet on potassium titanate	5-12
5.3.3	Photocatalytic decolouration of crystal violet	5-14
5.3.4	Supernatant turbidity.....	5-16
5.4	Conclusions	5-17
Chapter 6: Adsorption and photocatalytic degradation of methylene blue using potassium polytitanate and solar simulator6-1		
6.1	Introduction	6-2
6.2	Experimental.....	6-4
6.2.1	Materials	6-4
6.2.2	Photoreactor	6-4

6.2.3	Adsorption and photocatalysis.....	6-5
6.2.4	Regeneration of catalyst.....	6-6
6.3	Results and Discussion	6-6
6.3.1	Adsorption and photocatalytic decolourisation of MB and DOC removal	6-6
6.3.2	Mineralization of MB	6-9
6.3.3	Effect of operating conditions.....	6-10
6.3.3.1	Effect of MB concentration	6-10
6.3.3.2	Effect of catalyst loading.....	6-11
6.3.3.3	Effect of pH	6-12
6.3.3.4	Effect of light intensity	6-14
6.3.3.5	Regeneration of catalyst	6-17
6.4	Conclusion	6-17
Chapter 7: Adsorption behaviour of Pb(II) onto potassium Polytitanate nanofibre 7-1		
7.1	Introduction	7-2
7.2	Experimental.....	7-3
7.2.1	Materials	7-3
7.2.2	Adsorption experiment	7-4
7.2.3	Adsorption mechanism	7-6
7.2.4	Desorption and reusability studies	7-6
7.3	Results and Discussion	7-6
7.3.1	Effect of pH	7-6
7.3.2	Effect of adsorbent dose	7-9
7.3.3	Effect of initial concentration of Pb(II)	7-10

7.3.4	Comparison of potassium titanate with P25 for Pb(II) removal	7-11
7.3.5	Adsorption kinetics	7-12
7.3.6	Adsorption mechanism of Pb(II) onto titanate	7-14
7.3.7	Desorption and reusability studies	7-16
7.4	Conclusion	7-17
Chapter 8:	Conclusions and recommendations	8-1
8.1	Conclusions	8-2
8.1.1	Photodesorption of Organic Matter from Titanium Dioxide Particles in Aqueous Media.....	8-2
8.1.2	Synthesis and Characterisation of Potassium Poly titanate for Photocatalytic Degradation of Crystal Violet	8-3
8.1.3	Solar Simulator Assisted Photocatalysis of Methylene Blue using Potassium Poly titanate	8-5
8.1.4	Adsorption Behaviour of Pb(II) onto Potassium Poly titanate Nanofibre	8-6
8.2	Recommendations	8-7
Appendices.....	A-1	
Appendix A:	Sketch representing synthesis of potassium poly titanate	A-2
Appendix B:	Energy diffraction spectra of P25 and potassium poly titanate	A-3
Appendix C:	Adsorption/desorption isotherms of P25 and potassium poly titanate	A-5
Bibliography	B-1	

List of Figures

Figure 1-1. Photodesorption phenomena for water and waste water purification	1-6
Figure 2-1 Principle of photo activation of TiO ₂ semiconductor.	2-20
Figure 2-2: Formation mechanism of TiO ₂ nanotubes using hydrothermal method ...	2-39
Figure 2-3: Chemical structure of CV	2-50
Figure 2-4: Chemical structure of MB.....	2-51
Figure 2-5: Pathway of MB decomposition.....	2-53
Figure 3-1. SEM image to Degussa P25 titanium dioxide nanopowder.....	3-4
Figure 3-2. Zeta potential of 100 mg/L Degussa P25 suspension in MQ water.....	3-4
Figure 3-3. Recirculating photoreactor unit.....	3-9
Figure 3-4. Photo (left) and a schematic diagram (right) of batch reactor.	3-10
Figure 3-5. Photo and a schematic diagram of solar simulator.	3-11
Figure 3-6. Photo (left) and a schematic diagram (right) of hydrothermal autoclave.	3-12
Figure 3-7. Shimadzu UV-1700 spectrophotometer.....	3-14
Figure 3-8. A multi N/C 3100 analyser	3-14
Figure 3-9. LC-OCD analyser	3-15
Figure 3-10 Metrohm ion chromatograph.	3-16
Figure 3-11. MP-AES analyser.....	3-16
Figure 4-1. (a) Effect of recirculating flow rate on photodesorption of DOM and (b) the percentage of adsorption and photodesorption in relation to flow rate	4-7
Figure 4-2. (a) Effect of light intensity on the photodesorption of DOM and (b) the percentage of adsorption and photodesorption under different light intensities.....	4-9
Figure 4-3. (a) Effect of TiO ₂ loading on photodesorption of DOM and (b) the percentage of adsorption and photodesorption over different TiO ₂ loading	4-11

Figure 4-4. (a) Effect of organic loading on photodesorption of DOM and (b) the percentage of adsorption and photodesorption for different organic loadings	4-13
Figure 4-5. (a) Effect of SWW pH on photodesorption of DOM and (b) the percentage of adsorption and photodesorption for different solution pH	4-15
Figure 4-6. (a) Effect of individual organic constituents of SWW on photodesorption of DOM and (b) the percentage of adsorption and photodesorption for different organic constituents	4-18
Figure 4-7. LC-OCD chromatograms of DOM before treatment (black line), after adsorption (red line) and after photodesorption (blue line) for (a) SWW, (b) Beef extract. (c) Sodium lignin sulphonate. (d) Sodium lauryl sulphate. (e) Tannic acid. ...	4-21
Figure 4-8. Photodesorption of DOM (HMW and LMW organics) from TiO ₂ surface in SWW, (A) before adsorption, (B) after adsorption, (C) during photodesorption, (D) after photodesorption.	4-25
Figure 5-1. SEM images of the potassium titanate powders: as-prepared (A, B, and C) and calcined samples (AC, BC and CC).....	5-7
Figure 5-2. TEM images of potassium titanate powders: as-prepared (A, B, and C), and calcined samples (AC, BC and CC).....	5-8
Figure 5-3. Powder XRD patterns of Degussa P25 and of the as-prepared (A, B and C) and calcined samples (AC, BC and CC).....	5-11
Figure 5-4. (a) Decolouration of 10 mg/L CV solution by adsorption on as-prepared samples.....	5-13
Figure 5-5.(a) Decolourisation and (b) photodegradation of CV monitored by DOC analysis.....	5-16
Figure 5-6. Normalised decrease in the supernatant turbidity using prepared samples (A, B and C) and calcined samples	5-17

Figure 6-1. Kinetics of the (a) decolouration (UV-Vis absorbance at $\lambda = 664$ nm), and (b) photocatalytic degradation of MB	6-8
Figure 6-2. Evolution of sulphate ions during the photocatalytic degradation of MB over potassium polytitanate A, B, C, AC, BC and CC.	6-9
Figure 6-3. Effect of initial concentration of MB on the photodegradation efficiency ...	6-11
Figure 6-4. Effect of photocatalyst loading (0.01, 0.02, 0.05 and 0.1 g/L) on the removal of MB.	6-12
Figure 6-5. Effect of pH (4, 7 and 9) on the photodegradation of MB.	6-13
Figure 6-6. Effect of light intensity (5000, 15000 and 28000 Lux) on the photodegradation of MB.	6-14
Figure 6-7. Photocatalytic life cycle of potassium polytitanate 'A'.	6-17
Figure 7-1. Effect of solution pH on the adsorption of Pb(II) from solution.	7-8
Figure 7-2. Zeta potential of 10 mg/L suspension of potassium titanate and Pb(II).	7-8
Figure 7-3. Effect of titanate dose on the adsorption of Pb(II) from solution.	7-9
Figure 7-4. Effect of initial concentration of Pb(II) on the adsorption of Pb(II) from solution.	7-10
Figure 7-5. Comparison of potassium titanate with P25 on the adsorption of Pb(II) from solution.	7-11
Figure 7-6. The FTIR spectra of pure titanate and Pb(II) loaded titanate.	7-15
Figure 7-7. Ion exchange between K^+ and Pb^{+2} ions	7-15
Figure 7-8. Regeneration performance of titanate.	7-16

List of Tables

Table 2-1. Comparison of photocatalytic slurry-type and immobilised-type reactors	2-27
Table 2-2: Comparison of typical synthesis of titanate	2-33
Table 2-3: Assisted hydrothermal method for preparation of titanate nanotubes.....	2-47
Table 3-1. List of chemicals	3-2
Table 3-2. Synthetic wastewater constituents	3-3
Table 4-1. LC-OCD fractionation results of organic compounds, after adsorption and photodesorption	4-23
Table 5-1. Textural parameters of nanomaterials synthesis in this study	5-9
Table 5-2. Elemental composition of the as-prepared (A, B and C) and calcined samples (AC, BC and CC).....	5-11
Table 6-1. Apparent pseudo-first order kinetics for the photocatalytic degradation of MB over K-titanate ‘A’ under various operating conditions.....	6-16
Table 7-1. Kinetic parameters for the adsorption of Pb(II) onto titanate at 25°C.....	7-13

Abstract

Nanotechnology has great potential in advancing water and wastewater treatment to improve treatment efficiency. Several nanotechnology approaches to water purification are currently being investigated and some already are in use. Photocatalysis is a new advanced oxidation process based on the irradiation of semiconductor materials, normally TiO_2 , with UV light and has been demonstrated to be one of the “green” and more effective strategies for environmental remediation. Recently, photo-induced desorption of dissolved organic compounds in aqueous media during photocatalysis provides an exciting opportunity in wastewater treatment which significantly facilitates the regeneration of the adsorbent with low energy consumption. The scope of this research is to elucidate the photodesorption of organic matter from TiO_2 under UV irradiation. In addition, this research also includes synthesis of titania-based photocatalytic adsorbent nanomaterials produced by self-assembly for water purification. For this purpose, potassium titanate was synthesised using Degussa P25 as a titanium precursor in the presence of hydrogen peroxide as an oxidising agent and potassium hydroxide in alkaline solution via alkaline hydrothermal condition. As a part of nanotechnology, the development of the photocatalytic adsorbent nanofibre is of great importance to establish adsorption and photocatalytic water treatment an attractive and cost-effective process.

Photo-induced desorption of organic compounds from TiO_2 particles in aqueous media during photocatalysis has promising applications in water treatment. Photodesorption is a relatively fast phenomenon that facilitates the regeneration of photocatalysts with low energy consumption while concentrating the waste products in an energy and water efficient process. It has been proposed that this transport phenomenon involves a

significantly reduced affinity between the photocatalyst and pollutants upon UV illumination, and leads to the rapid detachment/decomposition of adsorbed pollutants.

Initially, organic matters were allowed to adsorb on the surface of the photocatalyst (Degussa P25) until adsorption equilibrium was achieved. When adsorption equilibrium had been reached, it was observed that photodesorption was observed shortly with UV-light illumination of TiO₂ before the bulk photocatalytic oxidation takes place. The effects of specific experimental conditions (pH, photocatalyst loading, organic loading, UV light irradiation, flow rate, specific organic compounds) on this phenomenon were also examined. The pH of the solution was found to influence both the adsorption and desorption percentages, thus revealing the role of particle charge on this phenomenon. Additionally, a 1 g/L loading of photocatalyst, 150 ml/min flow rate, 24 W light intensity showed an optimum photodesorption rate using a single strength synthetic wastewater at pH 7.

Photodesorption was observed only for sodium lauryl sulphate (50%), sodium lignin sulphonate (43.47%), beef extract (20.35%) and tannic acid (10.5%) indicating that photodesorption is specific to some organic compounds but not to all. Using liquid chromatography-organic carbon detection, untreated beef extract and sodium lignin sulphonate contained significant amounts of humic substances (~1,000 g/mol), which decreased in concentration after dark phase adsorption. A significant increase in low molecular weight (<350 g/mol) concentrations was observed after photodesorption. UV-treated sodium lauryl sulphate photodesorbed to give both higher molecular weight (HMW) and lower molecular weight (LMW) organics. Thus, the HMW fractions of organic compounds decomposed into smaller compounds after UV irradiation, which

subsequently desorbed from the TiO₂ surface. However, untreated tannic acid contained a larger proportion of LMW acids, which showed a high adsorption affinity to TiO₂ during adsorption and poorly desorbed upon irradiation.

Apart from an investigation on photodesorption, this research presents a synthesis of potassium titanate nanostructures by hydrothermal treatment of TiO₂ (P25) in KOH and H₂O₂. As-produced powders were characterised by scanning electron microscopy, energy-dispersive X-ray spectroscopy, transmission electron microscopy, X-ray diffraction, and nitrogen adsorption-desorption methods. Longitudinally-oriented-wire-like structures up to several micrometres in length and diameters ranging from 10 to 30 nm were obtained. BET surface area analysis indicates macroporous sized titanate with had 5-6 times larger specific surface area (235.81-330.10 m²/g) than the precursor P25. TEM images reflected belt-like structures of an isolated fibre with the presence of lattice fringes, which indicated a crystalline structure aligned with orientation of their basal nanobelts. The XRD spectra of potassium titanate were attributed to the transfer of a portion of anatase into mixed species of potassium titanate (K₂Ti₈O₁₇, K₂Ti₆O₁₃, K₂TiO₃ and K₃Ti₈O₁₇). They were recovered by calcining the specimens suggesting the possible existence of crystallisation sites under hydrothermal treatment in aqueous solution of H₂O₂ and KOH. Larger size fibrous nanowires resulting from the hydrothermal treatment demonstrated high affinity in adsorbing crystal violet (CV), which was mainly due to their high surface area. The photocatalytic bleaching of CV solution revealed that the wires are photoactive under UV light irradiation. Macroporous nanowires are considered to be effective adsorbents of CV, capable of its photocatalytic degradation, and they can be easily separated from the solution by settling.

Solar photocatalytic degradation of organic water pollutants can be used to destroy toxic organic pollutants in water. Hence, potassium titanate nanofibres synthesized by an aqueous peroxide route at high pH were examined as photocatalysts for the photodegradation of methylene blue (MB) using a solar simulator. The results show that potassium polytitanate nanofibres were effective adsorbents of MB and also facilitated its photocatalytic degradation. Sulphate ion evolution during photocatalysis confirms some mineralisation occurred and hence photo-oxidative degradation of MB. The optimum operational conditions for the photocatalytic degradation of MB were found at 0.05 g/L of photocatalyst, 10 mg/L MB and pH 7. The stability of a photocatalyst specimen was also studied for 3 degradation cycles using adsorption/photocatalysis model.

Potassium polytitanate nanofibres prepared via the hydrothermal method were investigated for their possible application in removing toxic metals from aqueous solution. Particular attention was paid to employing the titanate as novel effective adsorbents for the removal of Pb(II). Batch adsorption experiments demonstrated that the adsorption was influenced by various conditions such as solution pH, adsorbent dosage and initial Pb(II) concentration. The results showed that the adsorption rate was faster in the first 5 min and equilibrium was achieved after 180 min. The maximum amount of adsorption was detected at pH 5. Potassium titanate showed much higher adsorption capacity compared to P25. The kinetic studies indicated that the adsorption of Pb(II) onto titanate best fit the pseudo-second-order kinetic model. FTIR spectra revealed that the hydroxyl groups in titanate were responsible for Pb(II) adsorption. It was concluded that ion exchange and oxygen bonding may be the principal mechanisms

for the adsorption of Pb(II). The adsorption-desorption results demonstrated that the titanate could be readily regenerated after adsorption. Therefore the titanate exhibited great potential for removing of Pb(II) from wastewater.

List of publications included in the Thesis

Chapter 4

El Saliby, I., **Shahid, M.**, McDonagh, A., Shon, H.K. & Kim, J.-H. 2012, 'Photodesorption of organic matter from titanium dioxide particles in aqueous media', *Journal of Industrial and Engineering Chemistry*, vol. 18, no. 5, pp. 1774-80.

Shahid, M., Saliby, I.E., McDonagh, A., Kim, J.-H. & Shon, H.K. 2014, 'Photodesorption of specific organic compounds from titanium dioxide particles in aqueous media', *Desalination and Water Treatment*, vol. 52, no. 4-6, pp. 867-72.

Chapter 5

Shahid, M., El Saliby, I., McDonagh, A., Tijing, L.D., Kim, J.-H. & Shon, H.K. 2014, 'Synthesis and characterisation of potassium polytitanate for photocatalytic degradation of crystal violet', *Journal of Environmental Science* vol. 26, no. 11, pp. 2348-54).

Chapter 6

Shahid, M., El Saliby, I., McDonagh, A., Tijing, L.D., Kim, J.-H. & Shon, H.K. 2014, 'Adsorption and photocatalytic degradation of methylene blue using potassium polytitanate and solar simulator', (*Submitted to Journal of Nanoscience and Nanotechnology*).

Chapter 7

Shahid, M., El Saliby, I., McDonagh, A., Tijing, L.D., Kim, J.-H. & Shon, H.K. 2014, 'Adsorption behavior of Pb(II) onto Potassium Polytitanate Nanofibre', (*Abstract submitted to International Conference on Nano Science and Nano Technology 2014*).

Other publications during the PhD candidature*

Kim, J.B., Lee, K.W., Park, S.M., Shon, H.K., **Shahid, M.**, Saliby, I.E., Lee, W.E.,

Kim, G.-J. & Kim, J.-H. 2013, 'Preparation of Iron-Doped Titania from Flocculated Sludge with Iron-Titanium Composite Coagulant', *Journal of Nanoscience and Nanotechnology*, vol. 13, no. 6, pp. 4106-9.

Shahid, M., McDonagh, A., Kim, J.H. & Shon, H.K. 2014, 'Magnetised titanium dioxide (TiO₂) for water purification: preparation, characterisation and application', *Desalination and Water Treatment*, pp. 1-24.

Park, S.M., Chekli, L., Kim, J.B., **Shahid, M.**, Shon, H.K., Kim, P.S., Lee, W.-S., Lee, W.E. & Kim, J.-H. 2014, 'NO_x removal of mortar mixed with titania produced from Ti-salt flocculated sludge', *Journal of Industrial and Engineering Chemistry*, vol. 20, no. 5, pp. 3851-6.

Shahid, M., El Saliby, I., McDonagh, A., Tijing, L.D., Kim, J.-H. & Shon, H.K. 2014, 'Synthesis and Characterisation of Silica-modified Titania for Photocatalytic Decolouration of Crystal Violet', (Accepted for publication in *Journal of Nanoscience and Nanotechnology*).

*(not related to the Thesis)

Conference papers and presentations

El Saliby, I., **Shahid, M.**, McDonagh, A., Shon, H.K. & Kim, J.-H., 'Photodesorption of organic matter from titanium dioxide particles in aqueous media', Presented at the 4th International Conference on the “Challenges in Environmental Science and Engineering” (CESE-2011), 25-30 September 2011, Tainan City, Taiwan

Shahid, M., El Saliby, I., McDonagh, A., Kim, J.-H. & Shon, 'Synthesis and Characterisation of Silica-modified Titania for Photocatalytic Decolouration of Crystal Violet', Presented at the 5th International Conference on the “Challenges in Environmental Science and Engineering” (CESE-2012), 9-13 September 2012, Melbourne, Australia

Shahid, M., Saliby, I.E., McDonagh, A., Kim, J.-H. & Shon, H.K., 'Photodesorption of specific organic compounds from titanium dioxide particles in aqueous media', Presented at the 5th International Conference on the “Challenges in Environmental Science and Engineering” (CESE-2012), 9—13 September 2012, Melbourne, Australia

Shahid, M., El Saliby, I., McDonagh, A., Kim, J.-H. & Shon, H.K., 'Synthesis and Characterisation of Silica-modified Titania for Photocatalytic Decolouration of Crystal Violet', Presented at the 11th International conference on Nano Science and Nano Technology (ICNST 2013), 7-8 November 2013, Chosun University, Gwangju, Korea

Shahid, M., McDonagh, A., Kim, J.H. & Shon, H.K. 2014, 'Magnetised titanium dioxide (TiO₂) for water purification: preparation, characterisation and application', Presented at the 6th International Conference on the “Challenges in Environmental Science and Engineering” (CESE-2013), 29 October-2 November 2013, Daegu, Korea